

Coexistence of Spin Density Wave and Triplet Superconductivity

Wei Zhang and C. A. R. Sá de Melo

School of Physics, Georgia Institute of Technology, Atlanta, Georgia 30332

We discuss the possibility of coexistence of spin density wave (antiferromagnetism) and triplet superconductivity as a particular example of a broad class of systems where the interplay of magnetism and superconductivity is important. We focus on the case of quasi-one-dimensional metals, where it is known experimentally that antiferromagnetism is in close proximity to triplet superconductivity in the temperature versus pressure phase diagram. Over a narrow range of pressures, we propose an intermediate non-uniform phase consisting of alternating antiferromagnetic and triplet superconducting stripes. Within the non-uniform phase there are also changes between two and three dimensional behavior.

PACS numbers: 74.70.Kn, 74.25.DW

The competition or coexistence of magnetic order and superconductivity is a very important problem in condensed matter physics. There is a broad class of systems that present magnetic order and superconductivity in close vicinity. One of the most important systems are the Copper Oxides, where singlet superconductivity is found next to antiferromagnetism [1]. In addition, striped phases, where coexistence of antiferromagnetic order and singlet d-wave superconductivity, were observed in Copper Oxides [2]. Another system where magnetism and superconductivity are intertwined is Strontium Ruthenate, where the proximity to ferromagnetism has been argued as being important to the existence of triplet superconductivity in these materials [3]. Furthermore the newly discovered ferromagnetic superconductors $ZrZn_2$ and UGe_2 have stimulated a debate on the coexistence of ferromagnetism and triplet or singlet superconductivity [4, 5]. However, unlike any of these previous examples, we will discuss in this manuscript a system which may exhibit coexistence of antiferromagnetism (AF) and triplet superconductivity (TS).

New experiments on quasi-one-dimensional superconductors in high magnetic fields have shown that TS is strongly affected by the proximity to an AF phase characterized by insulating spin density wave (SDW) order [6]. From now on we will use interchangeably SDW and AF. Motivated by these experiments and the known phase diagram of quasi-one-dimensional (TMTSF) $_2$ PF $_6$ under pressure we propose a new phase for quasi-one-dimensional systems where AF (SDW) and TS coexist. The coexistence of these phases implies that the new state is non-uniform, with alternating stripes of SDW and TS, due to the appearance of a negative interface energy between SDW and TS regions. As indicated in the schematic phase diagram (Fig.1), the inhomogeneous intermediate phase is expected to exist over a narrow range of pressures $\Delta P = P_2(T) - P_1(T)$ around P_c , where $\Delta P \ll P_c$.

Effective Free Energy: The possibility of coexistence of SDW and TS in quasi-one-dimensional conductors transcends microscopic descriptions based on standard

g-ology, where SDW and TS phase boundaries neighbor each other but do not coexist [8]. Inspired by experiments [9, 10], we model (TMTSF) $_2$ PF $_6$ as a highly anisotropic orthorhombic crystal, and we take the primary directions of the SDW vector order parameter to be the b-axis (y-direction), and the primary direction of the TS vector order parameter to be the c-axis (z-direction). Furthermore, we consider the spatial variation of the SDW or TS order parameter to be along the a-axis (x-direction), as a reflection of the quasi-one-dimensionality of the system. This simplifies the choice of the order parameters to be $\mathbf{S}(\mathbf{r}) \rightarrow S_b(x)$, and $\mathbf{D}(\mathbf{r}) \rightarrow D_c(x)$, and reduces the associated effective field theory to one spatial dimension. Thus, the generalized Ginzburg-Landau Free energy in real space can be written as

$$\mathcal{F}_{tot} = \mathcal{F}_{AF} + \mathcal{F}_{TS} + \mathcal{F}_C, \quad (1)$$

where $\mathcal{F}_{AF}$, $\mathcal{F}_{TS}$, and $\mathcal{F}_C$ are the AF, TS and coupling contributions discussed below. The AF contribution is

$$\mathcal{F}_{AF} = \int_{L_{AF}} dx [U_{AF}(x) + V_{AF}(x)], \quad (2)$$

where $U_{AF}(x) = \alpha_{AF}|S_b(x)|^2 + \beta_{AF}|\partial_x S_b(x)|^2 + \gamma_{AF}|S_b(x)|^4$ represents a typical GL Free energy density, and $V_{AF} = \delta_{AF}|\partial_x S_b(x)|^4 + \theta_{AF}|S_b(x)|^2|\partial_x S_b(x)|^2$ represents the extra terms in the expansion, which are relevant close to $P_1(T)$ (Fig. 1). The TS contribution is

$$\mathcal{F}_{TS} = \int_{L_{TS}} dx [U_{TS}(x) + V_{TS}(x)], \quad (3)$$

where $U_{TS}(x) = \alpha_{TS}|D_c(x)|^2 + \beta_{TS}|\partial_x D_c(x)|^2 + \gamma_{TS}|D_c(x)|^4$ represents a typical GL Free energy density, and $V_{TS} = \delta_{TS}|\partial_x D_c(x)|^4 + \theta_{TS}|D_c(x)|^2|\partial_x D_c(x)|^2$ represents the extra terms in the expansion, which are relevant close to $P_2(T)$ (Fig. 1). To describe the coexistence region the two order parameters must couple. To conform with independent Parity invariance,

$$\mathcal{F}_C = \sum_{inter} \int_{\ell_p} dx \lambda'_{bc} |S_b(x)|^2 |D_c(x)|^2, \quad (4)$$

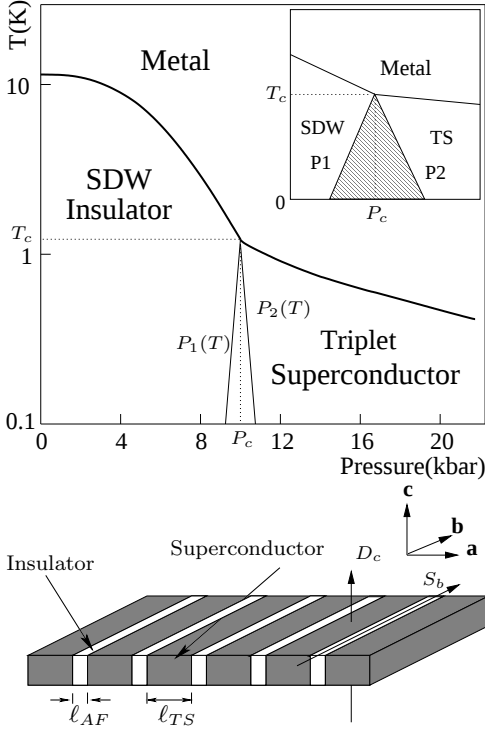


FIG. 1: a) Phase diagram of $(\text{TMTSF})_2\text{PF}_6$ in a log-linear scale (from [7]), showing schematically the proposed SDW-TS coexistence region (inset). b) Schematic drawing of the proposed stripe pattern for the SDW-TS coexistence region.

where the sum is over all interfaces between AF and TS, the coupling constant λ'_{bc} is pressure and temperature dependent, and ℓ_p is the proximity length over which AF and TS order parameters coexist locally. This length can be written as $\ell_p = \ell_{p,AF} + \ell_{p,TS}$, where $\ell_{p,AF}$ is the AF proximity length into the TS region, and $\ell_{p,TS}$ is the TS proximity length into the AF region (See Fig. 2). If $\lambda'_{bc} > 0$ it is more favorable for the AF and TS phases to phase-separate, however if $\lambda'_{bc} < 0$ an inhomogeneous phase with a large number of interfaces is favored, and the coexistence of AF and TS is possible.

In non-triplet systems local AF order and local singlet superconductivity (SS) can in principle coexist since AF order favors singlet correlations, and the proximity lengths on SS/AF systems can be small or large depending on the SS and AF materials [11, 12]. However, we are interested in TS and **not** in SS. In this case, it is well known that AF order is pair breaking to triplet electron pairs [13], and it is expected that $\ell_{p,AF}$ and $\ell_{p,TS}$ are small in comparison to the lengths of ℓ_{TS} and ℓ_{AF} of the TS and AF stripes, respectively. Only when the pressure P is close to the phase boundaries P_1 or P_2 (shown in Fig. 1) where ℓ_{TS} and ℓ_{AF} approach zero respectively, the proximity lengths $\ell_{p,TS}$ and $\ell_{p,AF}$ can be comparable to ℓ_{AF} and ℓ_{TS} . Using WKB [11] and the deGennes [14] extrapolation methods

the upper bound for ℓ_p is $\ell_p(P) \leq 0.1[\ell_{AF}(P) + \ell_{TS}(P)]$, and $\ell_{p,AF}(P) \leq 0.1\ell_{TS}(P_2)$ and $\ell_{p,TS}(P) \leq 0.1\ell_{AF}(P_1)$. Thus, extrapolating AF and TS order parameters in the proximity region by linear functions *à la* deGennes [14] leads to

$$\mathcal{F}_C = \sum_{inter} \lambda_{bc} |\partial_x S_b(x)|^2 |\partial_x D_c(x)|^2, \quad (5)$$

where $\lambda_{bc} = \lambda'_{bc} \int_0^{\ell_p} dx x^2 (\ell_p - x)^2$ is the new coupling constant. This coupling describes well the inhomogeneous phase where proximity effects between AF and TS stripes are weak, i.e., **away** but not too far from phase boundaries P_1 and P_2 .

Proximity effects will be important close to either phase boundary (P_1, P_2) as they may lead to further coupling between like-stripes. The inter-TS-stripe coupling (Josephson-type)

$$\mathcal{F}_{I,TS} = \sum_n \int_{overlap} dx \eta_{TS} |D_{c,n+1}(x) - D_{c,n}(x)|^2 \quad (6)$$

is significant for $P \approx P_2$, where the system changes from 2D to 3D TS. The inter-AF-stripe coupling

$$\mathcal{F}_{I,AF} = \sum_n \int_{overlap} dx \eta_{AF} |S_{b,n+1}(x) - S_{b,n}(x)|^2 \quad (7)$$

is significant for $P \approx P_1$, where the system changes from 3D to 2D AF. The domain of integration for both cases above is the overlap region between two consecutive AF or TS stripes respectively.

Saddle Point Equations: To obtain the saddle point equations, we consider $\mathcal{F}_C$, $\mathcal{F}_{I,AF}$ and $\mathcal{F}_{I,TS}$ perturbatively and minimize $\mathcal{F}_{tot}$ with respect to $S_b(x)$ and $D_c^*(x)$. Variations of $\mathcal{F}_{tot}$ with respect to $S_b(x)$ lead to the differential equation

$$[2\alpha_{AF} + 4\gamma_{AF} S_b^2(x) - \beta_{AF} \partial_x^2] S_b(x) + \hat{M}_{AF} S_b(x) = 0,$$

with $\hat{M}_{AF} S_b(x) = -\delta_{AF} \partial_x [(\partial_x S_b(x))^3 + 2\theta_{AF} S_b(x) |\partial_x S_b(x)|^2]$. Variations of $\mathcal{F}_{tot}$ with respect to $D_c^*(x)$ lead to a similar equation. In the case where $\lambda'_{bc}(P, T) < 0$, the formation of an inhomogeneous phase of alternating AF and TS stripes is preferred, and two additional transition lines (P_1, P_2) emanate from (P_c, T_c) . The presence of the inter-TS and inter-AF stripe Free energies indicates that $D_{n+1}(x) = D_n(x + x_0)$, and $S_{n+1}(x) = S_n(x + x_0)$ (in phase solutions), since η_{AF} and η_{TS} are both positive. For such inhomogeneous phase, the boundary conditions in the presence of AF-TS interfaces can be chosen as in deGennes method [14] by requiring that $S_b(x)|_{inter^+} = 0$ and $D_c(x)|_{inter^-} = 0$, where $inter^+$ and $inter^-$ denote the two boundaries limiting the region of locally coexisting $S_b(x)$ (AF) and $D_c(x)$ (TS) (See Fig. 2).

Variational Free Energy: We analyse $\mathcal{F}_{tot}$ variationally. We consider first the AF case and search for periodic solutions with period ℓ_{AF} , with $S_b(x)|_{inter^+} = 0$

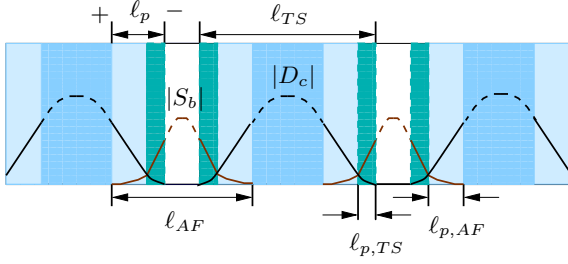


FIG. 2: Alternating AF and TS stripes with local coexistence region ℓ_p , which is defined by the region between *interface* $+$ and *interface* $-$ where AF and TS order parameters vanish. The length $\ell_p = \ell_{p,AF} + \ell_{p,TS}$, where $\ell_{p,AF}$ and $\ell_{p,TS}$ are AF and TS proximity lengths.

at the AF-TS interfaces. For a given volume of the AF region, controlled by L_{AF} , the Free energy associated with the AF phase becomes the sum of N_{AF} identical terms, where $N_{AF} = L_{AF}/\ell_{AF}$ gives the number of AF stripes. Generally, each term in $\mathcal{F}_{AF}$ corresponds to an insulating AF stripe characterized by the order parameter $S_b(x) = \sum_n A_n \sin(Q_n x)$, where $Q_n = 2\pi n/\ell_{AF}$. But here we take for simplicity the variational class where $S_b(x) = A_1 \sin(Q_1 x)$. To simplify notation, we will just use $A_1 \rightarrow A$ and $Q_1 \rightarrow Q$. In this case

$$\mathcal{F}_{AF} = L_{AF} [C_2(Q)A^2 + C_4(Q)A^4], \quad (8)$$

where $C_2(Q) = (\alpha_{AF} + \beta_{AF}Q^2)/2$ and $C_4(Q) = (3\gamma_{AF} + \theta_{AF}Q^2 + 3\delta_{AF}Q^4)/8$. The same type of analysis applies to $\mathcal{F}_{TS}$. In the absence of magnetic field, we assume periodic solutions of the form $D_c(x) = \sum_n B_n \sin(K_n x)$. As in the AF case we confine ourselves to a single component variational form $D_c(x) = B_1 \sin(K_1 x)$, and use the simplifying notation $B_1 \rightarrow B$ and $K_1 \rightarrow K$. Here B can be complex, but independent of position x . All the analysis discussed for the AF (SDW) case applies with the following change of notations: $L_{AF} \rightarrow L_{TS}$, $A \rightarrow B$, $Q \rightarrow K$, $\alpha_{AF} \rightarrow \alpha_{TS}$, $\beta_{AF} \rightarrow \beta_{TS}$, etc. Which in the TS case leads to:

$$\mathcal{F}_{TS} = L_{TS} [D_2(K)|B|^2 + D_4(K)|B|^4], \quad (9)$$

where $D_2(K) = (\alpha_{TS} + \beta_{TS}K^2)/2$ and $D_4(K) = (3\gamma_{TS} + \theta_{TS}K^2 + 3\delta_{TS}K^4)/8$. And the coupling Free energy is

$$\mathcal{F}_C = N_{int} \Lambda(Q, K, \ell_p) A^2 |B|^2, \quad (10)$$

where $N_{int} = 2N$ is the total number of interfaces, $f_{int} = \Lambda(Q, K, \ell_p) A^2 |B|^2$ is the Free energy of one interface with $\Lambda(Q, K, \ell_p) = \lambda'_{bc} \int_{\ell_p} dx |\sin(Qx) \sin[K(x_0 + x)]|^2$, where $x_0 = \ell_{TS} - \ell_p$.

Variational Solution: Variations of $\mathcal{F}_{tot}$ with respect to $\phi_{AF} = A$, $\phi_{TS} = |B|$, and $q_{AF} = Q$ or $q_{TS} = K$ lead to the non-trivial solutions

$$\phi_i^2 = \frac{4\beta_i \theta_i - 24\alpha_i \delta_i}{36\gamma_i \delta_i - \theta_i^2}, \quad (11)$$

$$q_i^2 = \frac{\alpha_i \theta_i - 6\beta_i \gamma_i}{\beta_i \theta_i - 6\alpha_i \delta_i}. \quad (12)$$

The width of each stripe then is given by

$$\ell_i = 2\pi \sqrt{\frac{\beta_i \theta_i - 6\alpha_i \delta_i}{\alpha_i \theta_i - 6\beta_i \gamma_i}}, \quad (13)$$

where $i = AF, TS$. In the case of $\lambda'_{bc} < 0$, the transition line $P_1(T)$ corresponds to the disappearance of the pure AF (SDW) phase, and the transition line $P_2(T)$ corresponds to the appearance of the pure TS phase. This implies that at $P_1(T)$ the TS stripe width is $\ell_{TS} = 0$, while at $P_2(T)$ the AF stripe width is $\ell_{AF} = 0$. Furthermore, for $P_1(T) < P < P_2(T)$, ℓ_{TS} (ℓ_{AF}) increases (decreases) with increasing pressure. In order to meet these and the saddle point requirements, the parameters appearing in $\mathcal{F}_{tot}$ must behave as follows. We define the reduced pressure changes $\Delta P_m = [P - P_m(T)]/P_c$, where $m = 1, 2$ and the density of states $N(E_F)$ at the Fermi energy E_F to analyse the AF and TS parameters. For $P < P_2(T)$, the AF parameters have the form $\gamma_{AF} = \gamma_1 N(\epsilon_F) T_c^2 > 0$; $\delta_{AF} = \delta_1 N(\epsilon_F) T_c^2 > 0$; $\eta_{AF} = \eta_1 N(\epsilon_F) T_c^2 > 0$; $\alpha_{AF} = \alpha_1 N(\epsilon_F) T_c^2 |\Delta P_2|^{\epsilon_{\alpha_{AF}}}$, with $\alpha_1 < 0$; $\beta_{AF} = \beta_1 N(\epsilon_F) T_c^2 |\Delta P_2|^{\epsilon_{\beta_{AF}}}$, with $\beta_1 < 0$; $\theta_{AF} = \theta_1 N(\epsilon_F) T_c^2 |\Delta P_2|^{\epsilon_{\theta_{AF}}}$, with $\theta_1 < 0$; and $36\gamma_{AF}\delta_{AF} - \theta_{AF}^2 > 0$. For $P > P_1(T)$, the TS parameters have the form $\gamma_{TS} = \gamma_2 N(\epsilon_F) T_c^2 > 0$; $\delta_{TS} = \delta_2 N(\epsilon_F) T_c^2 > 0$; $\eta_{TS} = \eta_2 N(\epsilon_F) T_c^2 > 0$; $\alpha_{TS} = \alpha_2 N(\epsilon_F) T_c^2 |\Delta P_1|^{\epsilon_{\alpha_{TS}}}$, with $\alpha_2 < 0$; $\beta_{TS} = \beta_2 N(\epsilon_F) T_c^2 |\Delta P_1|^{\epsilon_{\beta_{TS}}}$, with $\beta_2 < 0$; $\theta_{TS} = \theta_2 N(\epsilon_F) T_c^2 |\Delta P_1|^{\epsilon_{\theta_{TS}}}$, with $\theta_2 < 0$; and $36\gamma_{TS}\delta_{TS} - \theta_{TS}^2 > 0$. Consider now, the interface terms in the region $P_1(T) < P < P_2(T)$, which has the form $\lambda'_{bc} = \lambda_0 N(\epsilon_F) T_c^2 \text{sgn}[(P - P_1)(P - P_2)] |\Delta P_1|^{\epsilon_{\lambda_{AF}}} |\Delta P_2|^{\epsilon_{\lambda_{TS}}}$, with $\lambda_0 > 0$. This form is required to make the interface energy negative between $P_1(T)$ and $P_2(T)$.

Phase Boundaries: Next, we focus only on the analysis of ℓ_{AF} and $\mathcal{F}_{tot}$ in the vicinity of $P_2(T)$. We note in passing that the analysis of ℓ_{TS} and $\mathcal{F}_{tot}$ in the vicinity of $P_1(T)$ is entirely analogous. Under these considerations, as $P \rightarrow P_2(T)$ the size of the AF stripes is given by $\ell_{AF} \approx W_1 |\Delta P_2|^{(\epsilon_{\alpha_{AF}} - \epsilon_{\beta_{AF}})/2}$, where $W_1 = 2\pi(\alpha_1 \delta_1 / \beta_1 \gamma_1)^{1/2}$, when $\epsilon_{\beta_{AF}} + \epsilon_{\theta_{AF}} > \epsilon_{\alpha_{AF}}$, and $\epsilon_{\alpha_{AF}} + \epsilon_{\theta_{AF}} > \epsilon_{\beta_{AF}}$. The requirement that $\ell_{AF} \rightarrow 0$ as $P \rightarrow P_2(T)$ forces $\epsilon_{\alpha_{AF}} > \epsilon_{\beta_{AF}}$. Since the number of AF and TS stripes are the same $N_{AF} = N_{TS} = N$, where $N = L/(\ell_{AF}(P) + \ell_{TS}(P) - \ell_p(P))$, the number of interfaces is $N_{int} = 2N$. Therefore, the four contributions to $\mathcal{F}_{tot}$ in the coexistence region are $\mathcal{F}_{AF} = L_{AF} f_{AF}$, $\mathcal{F}_{TS} = L_{TS} f_{TS}$, $\mathcal{F}_C = 2N f_{int}$, $\mathcal{F}_{I,TS} = 2N f_{I,TS}$ with $L_{AF}(P) = N\ell_{AF}(P)$, $L_{TS} = N\ell_{TS}(P)$. As $P \rightarrow P_2$, the AF stripe length $\ell_{AF}(P) \rightarrow 0$, while the TS stripe length $\ell_{TS}(P) \rightarrow \ell_{TS}(P_2(T))$. Let us analyse the behavior of $\mathcal{F}_{tot}$ near $P_2(T)$ term by term. The AF part $\mathcal{F}_{AF}$ is the product of $L_{AF}(P) \approx L\ell_{AF}(P)/\ell_{TS}(P_2)$, where $\ell_{AF}(P) = \text{Const.} |\Delta P_2|^{(\epsilon_{\alpha_{AF}} - \epsilon_{\beta_{AF}})/2}$, and

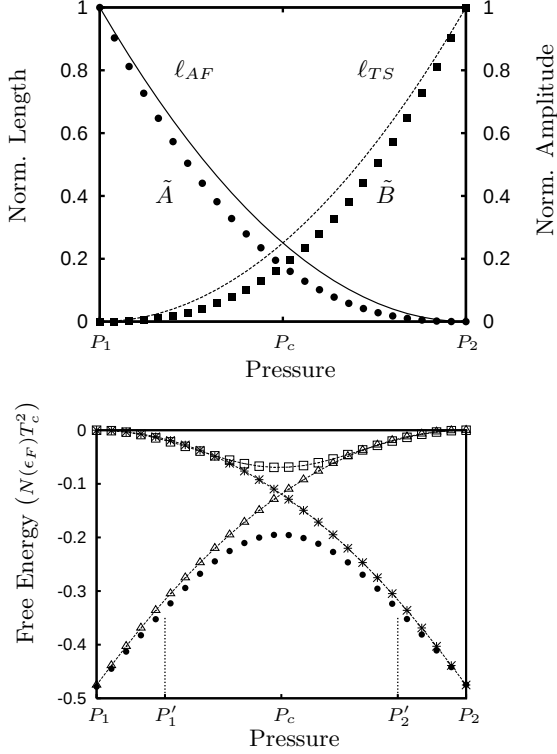


FIG. 3: a) Normalized amplitudes of the order parameters ($\tilde{A} = A/|A(P_1)|$, $\tilde{B} = B/|B(P_2)|$) and stripe lengths ℓ_{AF} and ℓ_{TS} normalized by $\ell_{AF}(P_1)$ and $\ell_{TS}(P_2)$, for exponents $\varepsilon_{\alpha_i} = 5.0$, $\varepsilon_{\beta_i} = 1.0$, $\varepsilon_{\theta_i} = 5.0$, where $i = AF, TS$ and dimensionless parameters: $\tilde{\alpha}_1 = \tilde{\beta}_1 = 1.0$, $\tilde{\gamma}_1 = 0.07$, $\tilde{\delta}_1 = 0.007$, $\tilde{\theta}_1 = -0.003$; and $\tilde{\alpha}_2 = \tilde{\beta}_2 = 1.0$, $\tilde{\gamma}_2 = 0.06$, $\tilde{\delta}_2 = 0.007$, $\tilde{\theta}_2 = -0.002$. b) Free energies for the coexistence and the pure AF and TS phases for the same parameters of a) and $\ell_p = 0.05(\ell_{AF} + \ell_{TS})$, $\varepsilon_{\lambda_i} = 1.0$, $\tilde{\lambda}_0 = -0.003$, and $\tilde{\eta}_1 = \tilde{\eta}_2 = 2.9 \times 10^{-6}$. Solid dots $\rightarrow \mathcal{F}_{tot}$; stars $\rightarrow Lf_{TS}$; triangles $\rightarrow Lf_{AF}$; squares $\rightarrow \mathcal{F}_C$. P'_1 indicates change from 3D to 2D AF, and P'_2 denotes change from 2D to 3D TS.

$f_{AF} = -Const.|\Delta P_2|^{2\varepsilon_{\beta_{AF}}}$, which leads to $\mathcal{F}_{AF} = -Const.|\Delta P_2|^{(\varepsilon_{\alpha_{AF}} + 3\varepsilon_{\beta_{AF}})/2}$. The TS part $\mathcal{F}_{TS}$ is the product of $L_{TS}(P) \approx L[1 - \ell_{AF}(P)/\ell_{TS}(P_2)]$ and $f_{TS}(P) \approx f_{TS}(P_2) < 0$, thus $\mathcal{F}_{TS} \approx \mathcal{F}_{TS}(P_2) + LConst.|\Delta P_2|^{(\varepsilon_{\alpha_{AF}} - \varepsilon_{\beta_{AF}})/2}$, where $\mathcal{F}_{TS}(P_2) = Lf_{TS}(P_2)$ is the Free energy of the pure triplet phase. Thus, for $P < P_2$, $\mathcal{F}_{TS}$ is increased with respect to the pure phase $\mathcal{F}_{TS}(P_2)$. Furthermore, $\mathcal{F}_C = -Const.|P_2 - P|^{\varepsilon_{\lambda_{AF}} + \varepsilon_{\beta_{AF}}}$ is negative, and $\mathcal{F}_{I,TS}$ is positive but proportional to a higher power of ΔP_2 . $\mathcal{F}_{AF}$ can be neglected in the vicinity of P_2 because it depends on a higher power of $|\Delta P_2|$ than that of $\mathcal{F}_{TS}$ or $\mathcal{F}_C$, when $\varepsilon_{\alpha_{AF}} > \varepsilon_{\beta_{AF}}$. For $\mathcal{F}_{tot}$ to be lower than that of the pure TS phase $\mathcal{F}_{TS}(P)$ it is necessary that the negative interface Free energy $\mathcal{F}_C$ dominates. This imposes the following requirement $\varepsilon_{\alpha_{AF}} \geq 3\varepsilon_{\beta_{AF}} + 2\varepsilon_{\lambda_{AF}}$. If $\varepsilon_{\lambda_{AF}} + \varepsilon_{\beta_{AF}} > 1$ the phase transition at P_2 is continuous. If $\varepsilon_{\lambda_{AF}} + \varepsilon_{\beta_{AF}} \leq 1$ the phase transition at P_2 is discontinuous. Similar

analysis close to P_1 leads to a continuous transition when $\varepsilon_{\lambda_{TS}} + \varepsilon_{\beta_{TS}} > 1$ and to a discontinuous transition when $\varepsilon_{\lambda_{TS}} + \varepsilon_{\beta_{TS}} \leq 1$. Thus, the point (P_c, T_c) can be bicritical, tricritical or tetracritical. In Fig. 3, we show the behavior of the various contributions to $\mathcal{F}_{tot}$ for the case where the transitions are continuous at P_1 and P_2 , and (P_c, T_c) is tetracritical. Dimensionless “volume” parameters are defined as $\tilde{\alpha}_i = \tilde{\beta}_i = \rho_i^{1/2}$, $\tilde{\gamma}_i = \gamma_i \sigma_i^{-1/2}$, $\tilde{\delta}_i = \delta_i \sigma_i^{3/2}$, $\tilde{\theta}_i = \theta_i \sigma_i^{1/2}$, “surface” ones are defined as $\tilde{\lambda}_0 = \lambda_0 \sigma_1^{-1/4} \sigma_2^{-1/4} (\ell_p(P_1) \sigma_1^{1/2})^5$, $\tilde{\eta}_i = \eta_i \sigma_i^{-1/2} (\ell_p(P_1) \sigma_1^{1/2})^3$, where $\rho_i = \alpha_i \beta_i$, $\sigma_i = \alpha_i / \beta_i$, and $i = 1, 2$.

Final Comments: A more realistic description of the system should include variations of SDW and TS order parameters along the y and z (transverse) directions, and be highly anisotropic but truly three dimensional. This is important for a renormalization group (RG) analysis and the determination of critical exponents in the case of continuous transitions.

Summary: We have proposed the possibility of coexistence of antiferromagnetism and triplet superconductivity in the phase diagram of $(\text{TMTSF})_2\text{PF}_6$. This intermediate phase is proposed to be inhomogeneous and to consist of alternating insulating AF and TS stripes [15] Two additional transition lines appear in a narrow range of pressures around P_c separating the coexistence region from the pure AF and pure TS phases. We estimate the maximum pressure range to be $\Delta P/P_c \approx 10\%$ at $T = 0$.

Acknowledgements: We thank NSF for support (DMR-0304380), and Ivan Bozovic for discussions.

-
- [1] E. Dagotto, Rev. Mod. Phys. **66**, 763-840 (1994)
 - [2] J. M. Tranquada, *et al.*, Phys. Rev. B **54**, 7489 (1996)
 - [3] Y. Maeno, *et al.*, Nature **372**, 532 (1994).
 - [4] C. Pfleiderer, *et al.*, Nature **412**, 58 (2001).
 - [5] S. S. Saxena, *et al.*, Nature **406**, 587 (2000).
 - [6] I. J. Lee, P. M. Chaikin, and M. J. Naughton, Phys. Rev. Lett. **88**, 207002 (2002).
 - [7] D. Jérôme, Mol. Cryst. Liq. Cryst. **79** 155 (1982).
 - [8] J. Solyom, Adv. Phys. **28**, 201 (1979).
 - [9] I. J. Lee, *et al.*, Phys. Rev. Lett. **88**, 017004 (2002)
 - [10] K. Mortensen, Y. Tomkiewicz, and K. Bechgaard, Phys. Rev. B **25**, 3319 (1982).
 - [11] I. Bozovic, *et al.*, Nature **422**, 873 (2003).
 - [12] C. Bell, *et al.*, Phys. Rev. B **68**, 144517 (2003)
 - [13] S. Nakajima, Prog. Theor. Phys. **50**, 1101 (1973).
 - [14] P. G. de Gennes, *Superconductivity of metals and alloys*, W. A. Benjamin, INC., New York (1966).
 - [15] After we submitted this manuscript to Physical Review Letters on July 2nd 2004, a SO(4) theory suggesting coexistence of AF and TS in Bechgaard salts appeared. [Daniel Podolsky, *et al.*, Phys. Rev. Lett. **93**, 246402 (2004).] However, the coexisting phase pattern was not predicted within the framework of the SO(4) theory.